

ND-A137 279

ACETYLENE DECOMPOSITION ON PD(100) AND PD(111): EELS
(ELECTRON ENERGY LOSS) (U) INDIANA UNIV AT BLOOMINGTON
DEPT OF PHYSICS L L KESMODEL 16 JAN 84 TR-9

1/1


UNCLASSIFIED

N00014-80-C-0147

F/G 7/4

NL



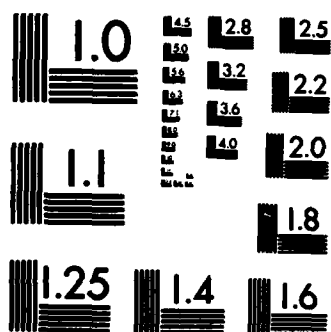

MICROCOPY RESOLUTION TEST CHART
NATIONAL BUREAU OF STANDARDS-1963-A

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

12

| REPORT DOCUMENTATION PAGE | | READ INSTRUCTIONS BEFORE COMPLETING FORM |
|--|-----------------------|--|
| 1. REPORT NUMBER Technical Report No. 9 | 2. GOVT ACCESSION NO. | 3. RECIPIENT'S CATALOG NUMBER |
| 4. TITLE (and Subtitle) Acetylene Decomposition on Pd(100) and Pd(111): EELS Evidence for CCH Formation | | 5. TYPE OF REPORT & PERIOD COVERED Interim |
| | | 6. PERFORMING ORG. REPORT NUMBER |
| 7. AUTHOR(s) L.L. Kesmodel | | 8. CONTRACT OR GRANT NUMBER(s) N00014-80-C-0147 |
| 9. PERFORMING ORGANIZATION NAME AND ADDRESS Indiana University Foundation Department of Physics Indiana University, Bloomington, IN 47405 | | 10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS |
| CONTROLLING OFFICE NAME AND ADDRESS Office of Naval Research Physics Program Office Arlington, Virginia 22217 | | 12. REPORT DATE January 16, 1984 |
| MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office) | | 13. NUMBER OF PAGES 5 |
| | | 15. SECURITY CLASS. (of this report) Unclassified |
| | | 15a. DECLASSIFICATION/DOWNGRADING SCHEDULE |

DISTRIBUTION STATEMENT (of this Report)

Approved for Public Release; Distribution Unlimited

DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)

DTIC
ELECTIC
JAN 26 1984
S
D

18. SUPPLEMENTARY NOTES

To be published in Journal of Vacuum Science and Technology A.
(Proceedings of the American Vacuum Society 30th National Symposium)

19. KEY WORDS (Continue on reverse side if necessary and identify by block number)

Acetylene; benzene; palladium (100) and (111) surfaces; vibrational spectroscopy; electron energy loss spectroscopy; chemisorption and catalysis; thermal decomposition; CCH formation.

20. ABSTRACT (Continue on reverse side if necessary and identify by block number)

→ The thermal decomposition of acetylene (C_2H_2) on palladium (100) and (111) surfaces in the temperature range 300-500K has been monitored with high-resolution electron energy loss spectroscopy (EELS). Vibrational analysis indicates predominant formation of rather stable CCH species on both surfaces. ←

DD FORM 1 JAN 73 1473

EDITION OF 1 NOV 65 IS OBSOLETE
S/N 0102-LF-014-6601UNCLASSIFIED
SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

84 01 26 016

AD A 137279

DTIC FILE COPY

OFFICE OF NAVAL RESEARCH

Contract N00014-80-C-0147

Technical Report No. 9

ACETYLENE DECOMPOSITION ON Pd(100) AND Pd(111):

EELS EVIDENCE FOR CCH FORMATION

by

L.L. Kesmodel
Department of Physics
Indiana University
Bloomington, Indiana 47405

16 January 1984

Reproduction in whole or in part is permitted for any
purpose of the United States Government.

Approved for Public Release; Distribution Unlimited

To be published in Journal of Vacuum Science and
Technology A Apr., Jun (1984) (Proceedings of the
American Vacuum Society 30th National Symposium,
Boston, 1983)

| | |
|--------------------|--|
| Accession For | |
| NTIS GRA&I | <input checked="checked" type="checkbox"/> |
| DTIC TAB | <input type="checkbox"/> |
| Unannounced | <input type="checkbox"/> |
| Justification | |
| By | |
| Distribution/ | |
| Availability Codes | |
| Dist | Avail and/or Special |
| A/1 | |



SUMMARY ABSTRACT: ACETYLENE DECOMPOSITION ON Pd(100) and
Pd(111): EELS EVIDENCE FOR CCH FORMATION

L.L. Kesmodel, Department of Physics, Indiana
University, Bloomington, Indiana 47405

Acetylene chemistry on palladium surfaces appears to be a complex and fascinating topic. Several recent ultraviolet photoemission (UPS) and thermal desorption (TDS) spectroscopic studies, for example, have indicated the formation of both benzene (C_6H_6) and ethylene (C_4H_4) on certain low index crystal faces of the material.¹⁻³ Sesselmann et al. have reported C_6H_6 formation on Pd(111) under conditions of low temperature and high exposure ($> 100L$) using TDS and UPS.¹ However, Tysoe et al. (UPS, TDS)² and Gentle and Muetterties³ (TDS) detected reactively-formed C_6H_6 at both low (230K) and high (500K) temperatures on Pd(111). The latter group also found evidence for the trimerization reaction on Pd(100) and Pd(110) but the reaction was reportedly more extensive on Pd(111).³ The above studies complement the earlier investigations of Gates and Kesmodel⁴ where CCH_2 , CCH_3 , and CH formation were reported from C_2H_2 thermal evolution on Pd(111) using vibrational analysis with high-resolution electron energy loss spectroscopy (EELS).

In view of the diversity of the above results concerning C_2H_2 low pressure surface chemistry on Pd surfaces we have undertaken more extensive EELS studies on both Pd(100) and Pd(111). A central issue we have addressed is the possible detection of reactively-formed C_6H_6 in the temperature range 300-500K. In this summary abstract we note the salient results

of this study. A complete discussion of this investigation will be presented elsewhere.⁵ We find C_2H_2 decomposition on both Pd(100) and Pd(111) is dominated by the formation of rather stable CCH species which persist to ~550K before additional dehydrogenation occurs. The chemistry on the (111) and (100) surfaces may be distinguished: On Pd(111) the formation of both CCH and ethylidyne ($\equiv C-CH_3$) occurs upon 300K C_2H_2 adsorption (with decomposition of ethylidyne near 450K). On Pd(100) C_2H_2 adsorbs associatively at 300K and forms CCH near 400K. No direct vibrational spectroscopic evidence for benzene formation was found in the present study.

The high-resolution EELS measurements were carried out with two 127° cylindrical deflection electron spectrometers. The Pd(111) experiments were performed with a single-pass instrument⁶ which is housed in an ion-pumped ultrahigh vacuum system (base pressure $\sim 1 \times 10^{-10}$ Torr). This instrument was operated at 10 meV (80 cm^{-1}) system resolution at typical elastic beam signal levels of $0.3-1.0 \times 10^5$ cps for hydrocarbon adsorption. The Pd(100) experiments employed a new double-pass spectrometer which achieves high signal levels at 2.5-10 meV system resolution.⁷ This instrument is incorporated in a diffusion/sublimation-pumped system (base pressure $\sim 5 \times 10^{-11}$ Torr). Due to the generally low intensity of the hydrocarbon modes the spectrometer was operated at 8-9 meV ($64-72 \text{ cm}^{-1}$) system resolution at typical elastic beam count rates of 2×10^6 cps. Sample preparation and cleaning have been described elsewhere.⁴

A summary of basic EELS experiments carried out on both

(111) and (100) surfaces is listed below. Unless noted otherwise the spectra were obtained under specular scattering conditions:

- (1) C_2H_2 (C_2D_2) adsorption (300K) and thermal processing (300-600K);
- (2) C_6H_6 (C_6D_6) adsorption (300K) and thermal processing (300-600K);
- (3) Off-specular EELS comparison of acetylene-derived surface species (450-475K) and benzene (Pd(100) only);
- (4) $C_2H_2 + C_2D_2$ isotope mixing (300-500K);
- (5) $C_6H_6 + D_2$; $C_6D_6 + H_2$ isotope mixing (150-500K) (Pd(111) only).

In the course of these studies it was found that the surface species which remains after annealing 300K chemisorbed C_2H_2 to 450K exhibited major vibrational features similar to C_6H_6 . Representative spectra for Pd(100) to illustrate this aspect are shown in Fig. 1. Spectrum 1(a) is due to associatively chemisorbed acetylene. Spectra 1(b) and 1(c) both exhibit strong CH bending losses ca. $730-750\text{ cm}^{-1}$ and weak CH stretching losses ca. $3000-3020\text{ cm}^{-1}$. However, detailed comparison of the weaker losses, including off-specular analysis, clearly differentiates between the 450K C_2H_2 -derived species and chemisorbed C_6H_6 . Particularly conclusive were the isotope-mixing experiments noted above which favored a CH or CCH species. The presence of a CC stretching mode ca. 1340 cm^{-1} in both C_2H_2 and C_2D_2 derived species rules against CH and leaves CCH as the most probable interpretation of the spectra. The carbon-carbon bond order deduced from the CC and CH stretching frequencies is between 1 and 2, indicating that both carbon atoms are involved in the CCH interaction with the metal surface.

I thank Dr. J.E. Demuth for numerous stimulating


discussions. This work was supported by the Office of Naval Research.

References

1. W. Sessellmann, B. Woratschek, G. Ertl, J. Kuppers, and H. Haberland, Surface Sci., to be published.
2. W.T. Tysoe, G.L. Nyberg, and R.M. Lambert, Surface Sci., to be published.
3. T.M. Gentle and E.L. Muettertides, J. Phys. Chem. 87 (1983) 2469.
4. J.A. Gates and L.L. Kesmodel, Surface Sci. 124 (1983) 68.
5. L.L. Kesmodel, D.W. Waddill, and J.A. Gates, to be published.
6. L.L. Kesmodel, J.A. Gates, and Y.W. Chung, Phys. Rev. B23 (1981) 489.
7. L.L. Kesmodel, J. Vacuum Sci. Technol., in press.

Figure Caption

Fig. 1: High-resolution EELS spectra for hydrocarbon adsorption on Pd(100).

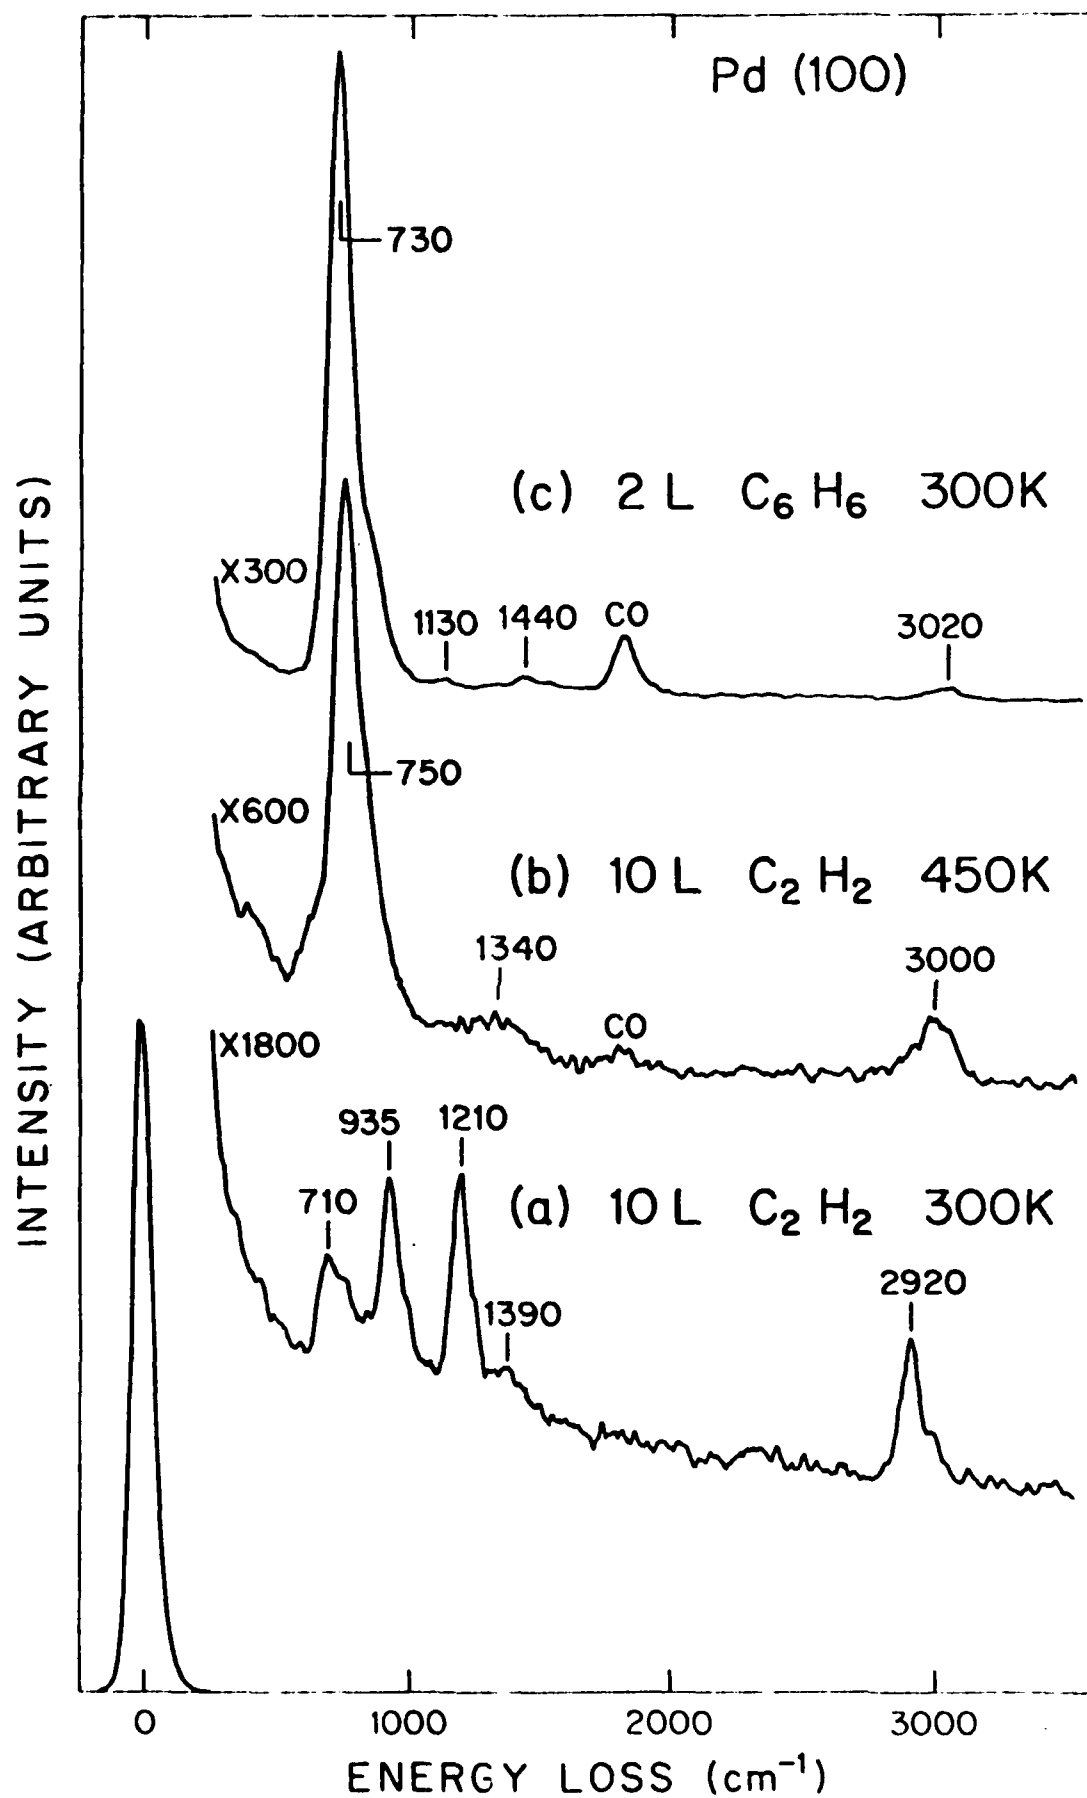

FILMED

02 - 84